

# COLD WORK STEELS

## Available Product Shapes

Flat Bar	Ground Flat	Long Products	Open Die Forgings	Plates
Round Bar	Round Ground Bar			

## Product Description

BÖHLER K890 MICROCLEAN – This powder-metallurgical cold-working steel has good toughness, very good compressive strength, and excellent fatigue strength.

## Properties

A powder metallurgy cold work tool steel with an outstanding capacity for plastic yield and a high fatigue strength.

## Applications

- > Machine knife (for producers)
- > Coining
- > General Components for Mechanical Engineering
- > Fine Blanking, Stamping, Blanking
- > Rolling
- > Powder Pressing
- > Components for Recycling Industry
- > Cold Forming
- > Wear parts
- > Pill punching dies

## Chemical composition (wt. %)

C	Si	Mn	Cr	Mo	V	W	Co
0.85	0.55	0.40	4.35	2.80	2.10	2.55	4.50

### Material characteristics

	Compressive strength	Dimensional stability during heat treatment	Toughness	Wear resistance abrasive	Wear resistance adhesive
<b>BÖHLER K890</b> MICROCLEAN®	★★★★	★★★★★	★★★★★	★★★	★★★
<b>BÖHLER K100</b>	★★	★★	★	★★★	★★
<b>BÖHLER K105</b>	★★	★★	★	★★	★★
<b>BÖHLER K107</b>	★★	★★	★	★★★	★★
<b>BÖHLER K110</b>	★★	★★★	★	★★★	★★
<b>BÖHLER K190</b> MICROCLEAN®	★★★★	★★★★★	★★★★	★★★★	★★★★
<b>BÖHLER K294</b> MICROCLEAN®	★★★★★	★★★★★	★★★	★★★★★	★★★★★
<b>BÖHLER K340</b> ISODUR®	★★★	★★★★	★★★	★★★	★★★★
<b>BÖHLER K340</b> ECOSTAR®	★★★	★★★	★★	★★	★★
<b>BÖHLER K360</b> ISODUR®	★★★	★★★★	★★★	★★★★	★★★★
<b>BÖHLER K346</b>	★★★	★★★	★★★	★★★★	★★
<b>BÖHLER K353</b>	★★	★★★	★★	★★	★★
<b>BÖHLER K390</b> MICROCLEAN®	★★★★★	★★★★★	★★★★	★★★★★	★★★★★
<b>BÖHLER K490</b> MICROCLEAN®	★★★★	★★★★★	★★★★	★★★★	★★★★
<b>BÖHLER K497</b> MICROCLEAN®	★★★★★	★★★★★	★★★	★★★★★	★★★★★


### Delivery condition

Annealed	
Hardness	max. 280 HB

### Heat treatment

Soft annealing		
Temperature (°C   °F)	650   1202 to 700   1292	Depending on the application, hardness can be adjusted by using specialized annealing treatment.
Stress relieving		
Temperature (°C   °F)	650   1202 to 700   1292	After through-heating, soak for 1 to 2 hours in a neutral atmosphere. Slow cooling in furnace.
Hardening and Tempering		
Temperature (°C   °F)	1070   1958 to 1150   2102	Following temperature equalisation: 20-30 minutes for a hardening temperature of 1070 - 1100 °C (1960 - 2010 °F) 6 minutes for a hardening temperature of 1150 °C (2100 °F) After hardening, tempering to the desired working hardness, see tempering chart.

## Tempering chart

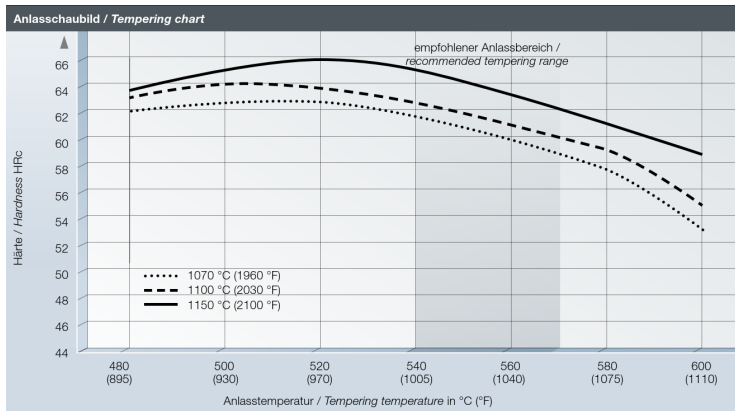

### Tempering:

Hardening temperature:  
 ••• 1070°C/1960°F  
 - - - 1100°C/2030°F  
 ——— 1150°C/2100°F

## Physical Properties

Temperature (°C   °F)	20   68
Density (kg/dm <sup>3</sup>   lb/in <sup>3</sup> )	7.85   0.28
Thermal conductivity (W/(m.K)   BTU (IT) ft/hr/ft <sup>2</sup> /F)	22.5   13
Specific heat (J/(kg.K)   BTU (IT) lb/F)	450   107.48
Spec. electrical resistance (Ohm.mm <sup>2</sup> /m   10 <sup>-4</sup> Ohm.inch <sup>2</sup> /ft)	0.5   2.36
Modulus of elasticity (10 <sup>3</sup> N/mm <sup>2</sup>   10 <sup>3</sup> ksi)	218   31.56

## Thermal Expansions

Temperature (°C   °F)	100   212	200   392	300   572	400   752	500   932	600   1112	700   1292
Thermal expansion (10 <sup>-6</sup> m/(m.K)   10 <sup>-6</sup> inch/(inch.F))	10.5   5.833	11   6.111	11.3   6.278	11.7   6.5	12.1   6.722	12.4   6.889	12.9   7.167

For more information see [www.voestalpine.com/boehler-edelstahl](http://www.voestalpine.com/boehler-edelstahl)

The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.

voestalpine BÖHLER Edelstahl GmbH & Co KG

Mariazeller Straße 25

8605 Kapfenberg, AT

T. +43/50304/20-0

E. [info@boehler-edelstahl.at](mailto:info@boehler-edelstahl.at)

[www.voestalpine.com/boehler-edelstahl](http://www.voestalpine.com/boehler-edelstahl)

voestalpine

ONE STEP AHEAD.